

Synthesis and Characterization of WO₃ thin films deposited by Thermal Evaporation Technique

Kakade SB, Thorat SM, Maske SS, Mandhare PL, Kumbhar KS, Kale RD, Kalange AE

Thin Film Laboratory, Tuljaram Chaturchand College, Baramati Dist.: Pune, India

Email: kalangeashok@gmail.com

Manuscript Details

Available online on <https://www.irjse.in>
ISSN: 2322-0015

Editor: Dr. Arvind Chavhan

Cite this article as:

Kakade SB, Thorat SM, Maske SS, Mandhare PL, Kumbhar KS, Kale RD, Kalange AE. Synthesis and Characterization of WO₃ thin films deposited by Thermal Evaporation Technique, *Int. Res. Journal of Science & Engineering*, 2023, Special Issue A12: 33-37.
<https://doi.org/10.5281/zenodo.7794391>

Article published in Special issue of International Conference on "Recent Trends in Materials Science, Synthesis, Characterization and Applications (RTMS-2023)" organized by Department of Physics, Anekant Education Society's, Tuljaram Chaturchand College of Arts, Science and Commerce, Baramati, Dist Pune, Maharashtra, India (Autonomous) date, January 3-4, 2023.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

Abstract

Thin films of tungsten oxide (WO₃) have been extensively explored as electrochromic materials and have a wide range of uses in electrochromic devices, smart windows, gas sensors, and optical windows. In the present study, the optical, structural and morphological characteristics of WO₃ thin films were investigated. The WO₃ films, were synthesized on glass substrate using the thermal evaporation method under a pressure of 10⁻⁵ mbar. The prepared films were characterized by X-ray diffractometer, Fourier transform infrared spectroscopy (FTIR), UV-visible photo spectroscopy, Field emission scanning electron microscopy (FESEM).

Keywords: Tungsten oxide, Thermal Evaporation, gas sensors.

Introduction

Recent years have seen a surge in research into metal oxide thin films due to their electrical characteristics, stability at high temperatures, and endurance. Many researchers have investigated metal oxide thin films as electronic materials due to their structural simplicity and low cost. [1] However, to enhance such devices, it is important to completely comprehend the surface flaws and thin film properties that are prevalent during the film fabrication operations. [2] For gas sensing applications, semiconductor metal oxides (WO₃, TiO₂, MgO, and MoO₃) have been extensively Studies. The characteristics and functionality of the gas sensor are anticipated to be improved by these metal oxides with specific nanostructures such nanorods, nanowires, and other nano dimensions [3].

In recent years semiconducting oxide materials like WO_3 have been the subject of intense research due to their low cost, high stability, and ease of sensor fabrication. In recent years semiconducting oxide materials like WO_3 have been the subject of intense research due to their low cost, high stability, and ease of sensor fabrication.[4] Among the transition metal oxides Pure WO_3 and thick coatings of metal tungstate[5] have been found to have exceptional sensitivity to nitrogen oxides at low and high operating temperatures, respectively. [6] Tungsten oxide (WO_3) is an n-type wide band gap metal oxide semiconductor. Due to its intrinsic electrical conductivity, good sensitivity, and selectivity toward various gases like NO_2 , WO_3 has emerged as a potential material for gas sensing devices, joining other metal oxides including SnO_2 , TiO_2 , In_2O_3 , and ZnO . [7-8] It is well known that the deposition method and preparation conditions affect the film characteristics. Different techniques, including sol-gel, electro deposition, pulsed laser, sputtering, and spray pyrolysis, were used to prepare WO_3 thin films. [9-14] Additionally, there are conventional methods including thermal evaporation, chemical deposition, and electron beam evaporation. [15-17] In this research, WO_3 thin films were deposited using the high vacuum thermal evaporation from WO_3 powder. The obtained thin films are characterized by using x-ray diffractometer (XRD), UV-Visible spectrophotometer and field emission scanning electron microscopy (FESEM).

Methodology

Synthesis of tungsten oxide thin films:

Tungsten oxide thin films were synthesized by a thermal evaporation technique. The commercially available high purity WO_3 powder (99.9%) was deposited silicon substrates by evaporation in a high vacuum chamber using a molybdenum boat filament. Before the deposition, the powders were placed in desiccator to avoid any moisture and decontamination. Ultrasonically cleaned glass slides were used as substrates. The substrates were mounted on a substrate holder which was placed at a distance of 30 cm in line of sight from the evaporation source. The tungsten trioxide

(WO_3) thin films were prepared at room temperature (300K) by the thermal evaporation techniques using a commercial vacuum coating unit (Hind Hivac 12A4D). A diffusion pump backed by a rotary pump was employed to produce the ultimate pressure of 10^{-5} mbar. Deposition was carried out at 10^{-5} mbar. The tungsten oxide got evaporated and directly deposited over the substrate kept at low temperature region. The samples were mounted on a stainless-steel block on a transfer arm. The system was allowed to achieve high vacuum. The molybdenum boat holding the WO_3 powder was slowly heated. The WO_3 powder inside the boat vaporized when the power was applied and the vapour phase was condensed on the substrate at room temperature. The structural, optical and morphological studies were performed on synthesized thin films.

Characterization Techniques:

The crystalline structure of as-deposited WO_3 films were studied with an X-ray diffractometer. X-ray diffraction patterns of the thin films deposited on glass substrates were recorded by Rikagu miniflex diffractometer equipped with $\text{Cu-K}\alpha$ radiation ($\lambda=1.54056 \text{ \AA}$) in a wide range of Bragg's angles 2θ from 10° to 80° at a scanning rate of 2° per minute. The field-emission scanning electron microscopy (FESEM) was carried out to characterize the surface morphologies of the prepared WO_3 thin films deposited on glass substrates. The optical absorption and transmission in the wavelength range 200 – 800 nm were recorded by using a double beam spectrophotometer (UV-VIS Shimadzu). The phase composition was investigated by Fourier Transform Infrared spectroscopy using Vertex 70 spectrophotometer, with a resolution of 4 cm^{-1} over a wavenumber range of $400\text{-}4000 \text{ cm}^{-1}$.

Result and Discussion

Structural Properties:





1. X-Ray Diffraction (XRD)

To determine the crystalline phase and crystallinity, the structural characteristics of WO_3 were investigated by using X-ray diffraction (XRD). The XRD pattern of the

deposited WO_3 thin films on glass substrate is shown in figure 1. It demonstrates that there are no clear diffraction peaks of the crystalline tungsten oxides, only a widened peak with an amorphous characteristic in the range of Bragg's angles 2θ from 10° to 80° is observed. This is consistent with previously published research. [18-19] The XRD analysis indicates that the as-prepared thin films almost consist of amorphous nature of tungsten trioxide. This may be explained by the fact that for WO_3 thin films crystal lattice alignment and crystallization are not initiated on amorphous glass substrates at ambient temperature. [19].

2. Fourier Transform Infrared Spectroscopy (FTIR)

FTIR measurement was taken to identify the various functional groups that were present in the sample and to learn more about its crystal structure. Figure 2 is the infrared spectrum of WO_3 reveals a broad band with distinctive frequency vibrations between 400 and 4000 cm^{-1} . [20-[21] The band at 540 cm^{-1} is attributed to W-O stretching vibrations, while the band at 626 cm^{-1} is assigned to the W-O-W bridging modes of the WO_6 (octahedral) corner sharing species. The band at 918 cm^{-1} is observed in the range of (Metal=Oxygen) vibrations, which is characteristic for stretching vibrations of W=O bond.

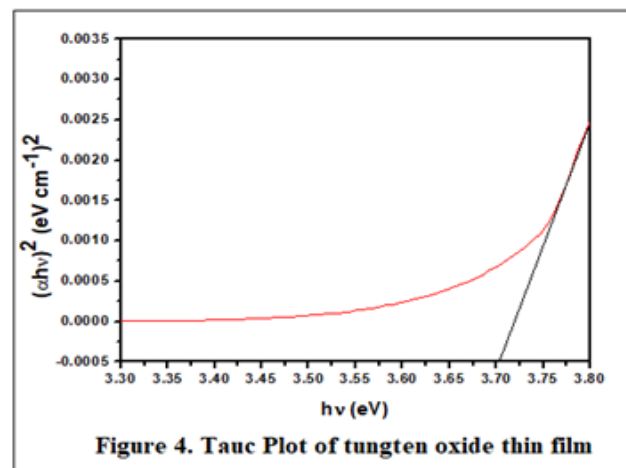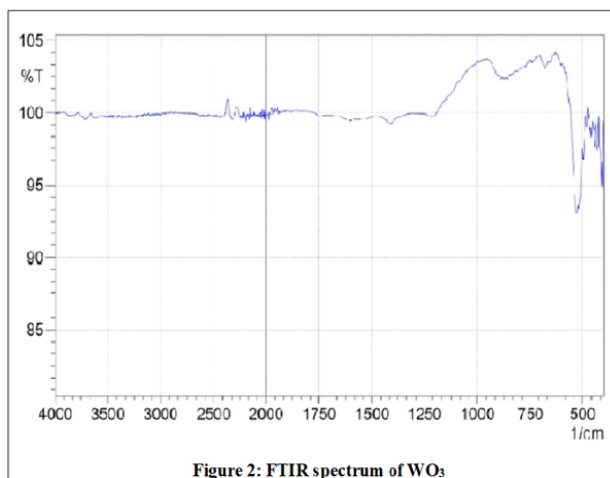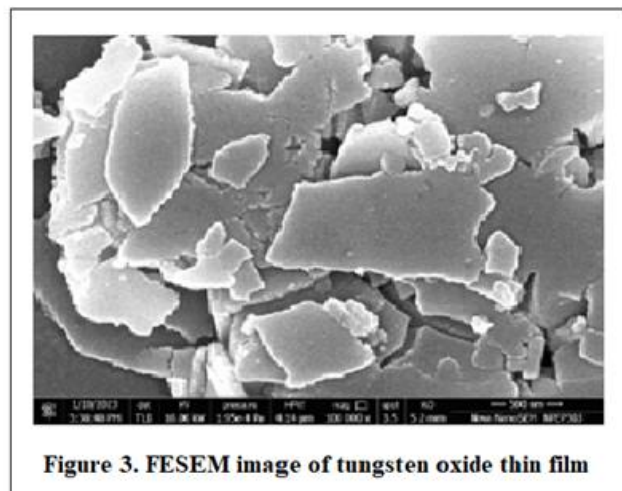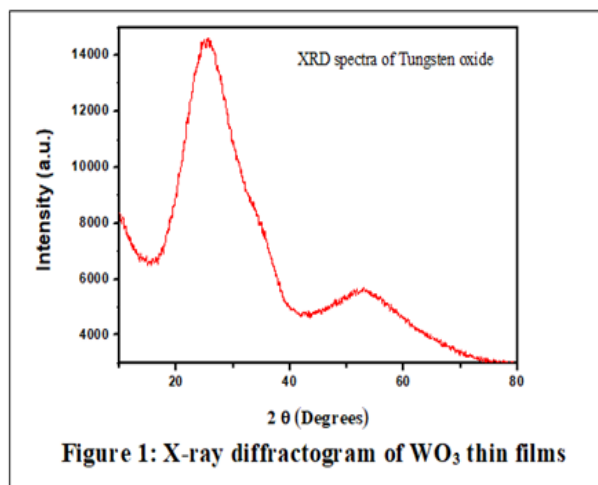

a. Morphological Properties:

The field emission scanning electron microscope has been used to examine the surface morphology of WO₃ thin films (FESEM). Figure 3 shows a FESEM image of the WO₃ thin film. The formation of stacks of WO₃ platelets on the glass surface with various sizes is depicted in FESEM image of deposited WO₃ thin films. [22] These reveals the layered growth of the WO₃ thin film on the surface. The platelet formation of WO₃ thin film on glass surface was described by Karuppasamy et al. [23].

b. Optical Properties:

In the wavelength range of 200-800 nm, the optical absorption spectra of WO₃ films have been recorded. Figure 4 shows the Tauc plot of $(\alpha h\nu)^2$ versus photon energy ($h\nu$) of the deposited WO₃ thin film, where h is the plank's constant, ν is the frequency of the incoming radiation, and α is the absorption coefficient. Optical bandgap of the WO₃ thin film was calculated from the linear portion of the Tauc plot. Linear region is clearly seen in figure at $h\nu > 3.5$ eV for WO₃ thin film which is in accordance with the well-known absorption law $\alpha h\nu \sim (h\nu - E_g)^{1/2}$ being characteristic for direct optical transitions. [24] Estimated value of bandgap of the WO₃ thin film is found to be 3.70 eV and is close to the reported value. [25]

Conclusion

In a present study we have carried out deposition of WO₃ thin film by the thermal vacuum evaporation technique on glass substrates. The structural, surface morphological and optical properties of the deposited films were studied. The structural properties of deposited film were investigated by using XRD. The XRD patterns clearly indicates that the prepared WO₃ thin films have amorphous characteristics. FTIR bands present more evidence of the best quality and the high purity of WO₃ thin films. The surface morphological study shows the formation of platelets of WO₃ on the glass surface with different sizes. The UV-Visible characterization reveals that optical bandgap of the WO₃ was found to be 3.7 eV at ambient temperature.

This method of thermal evaporation can be used for synthesis of thin films of other metals, alloys and oxides by optimizing parameters like current, temperature, source to substrate distance.

Future research involved the deposition of various metal oxide thin films, including SnO₂, TiO₂, InO₂, MoO₃, CeO₂, etc., on conducting and non-conducting substrates for a variety of purposes, including gas sensors, solar cells, optical coatings, etc.

Conflicts of interest: The authors stated that no conflicts of interest.

References

1. C. A. Papadopoulos, D. S. Vlaehos, and J. N. Avaritsiotis, "Comparative study of various metal-oxide-based gas-sensor architectures," 1996.
2. D.-M. Na, L. Satyanarayana, G.-P. Choi, Y.-J. Shin, and J. S. Park, "Surface Morphology and Sensing Property of NiO-WO₃ Thin Films Prepared by Thermal Evaporation," *Sensors*, vol. 5, pp. 519-528, 2005, [Online]. Available: <http://www.mdpi.org/sensors>
3. R. Senthilkumar, G. Ravi, C. Sekar, M. Arivanandhan, M. Navaneethan, and Y. Hayakawa, "Determination of gas sensing properties of thermally evaporated WO₃ nanostructures," *Journal of Materials Science: Materials in Electronics*, vol. 26, no. 3, pp. 1389-1394, Mar. 2015, doi: 10.1007/s10854-014-2552-4.
4. A. Arfaoui, S. Touihri, A. Mhamdi, A. Labidi, and T. Manoubi, "Structural, morphological, gas sensing and photocatalytic characterization of MoO₃ and WO₃ thin films prepared by the thermal vacuum evaporation technique," *Appl Surf Sci*, vol. 357, pp. 1089-1096, Dec. 2015, doi: 10.1016/j.apsusc.2015.09.124.
5. J. Tamaki, T. Fujii, K. Fujimori, N. Miura, and N. Yamazoe, "Application of metal tungstate-carbonate composite to nitrogen oxides sensor operative at elevated temperature," 1995.
6. C. Cantalini *et al.*, "B Cross sensitivity and stability of NO₂ sensors from WO₃ thin film," 1996.
7. M. Ahsan, T. Tesfamichael, M. Ionescu, J. Bell, and N. Motta, "Low temperature CO sensitive nanostructured WO₃ thin films doped with Fe," *Sens Actuators B Chem*, vol. 162, no. 1, pp. 14-21, Feb. 2012, doi: 10.1016/j.snb.2011.11.038.



8. D.-S. Lee, K.-H. Nam, and D.-D. Lee, "Effect of substrate on NO-sensing properties of WO₃ thin film gas sensors," 2000.
9. M. Deepa, P. Singh, S. N. Sharma, and S. A. Agnihotry, "Effect of humidity on structure and electrochromic properties of sol-gel-derived tungsten oxide films," *Solar Energy Materials and Solar Cells*, vol. 90, no. 16, pp. 2665–2682, Oct. 2006, doi: 10.1016/j.solmat.2006.02.032.
10. M. Deepa, M. Kar, and S. A. Agnihotry, "Electrodeposited tungsten oxide films: Annealing effects on structure and electrochromic performance," *Thin Solid Films*, vol. 468, no. 1–2, pp. 32–42, Dec. 2004, doi: 10.1016/j.tsf.2004.04.056.
11. A. Rougier, F. Portemer, A. Quede, M. el Marssi, F. F. Francé, and F. F. Francé, "Characterization of pulsed laser deposited WO₃ thin films for electrochromic devices." [Online]. Available: www.elsevier.nl/locate/apsusc
12. B. Gavanier, N. S. Butt, M. Hutchins, V. Mercier, A. J. Topping, and J. R. Owen, "A comparison of the electrochemical properties of lithium intercalated amorphous and crystalline tungsten oxide."
13. M. Regragui et al., "Preparation and characterization of pyrolytic spray deposited electrochromic tungsten trioxide @lms." [Online]. Available: www.elsevier.com/locate/tsf
14. M. M. El-Nahass, M. M. Saadeldin, H. A. M. Ali, and M. Zaghlol, "Electrochromic properties of amorphous and crystalline WO₃ thin films prepared by thermal evaporation technique," *Mater Sci Semicond Process*, vol. 29, pp. 201–205, 2015, doi: 10.1016/j.mssp.2014.02.051.
15. C. E. Tracy and D. K. Benson, "Preparation of amorphous electrochromic tungsten oxide and molybdenum oxide by plasma enhanced chemical vapor deposition," *Journal of Vacuum Science & Technology A: Vacuum, Surfaces, and Films*, vol. 4, no. 5, pp. 2377–2383, Sep. 1986, doi: 10.1116/1.574080.
16. A. Antonaia, T. Polichetti, M. L. Addonizio, S. Aprea, C. Minarini, and A. Rubino, "Structural and optical characterization of amorphous and crystalline evaporated WO₃ layers." [Online]. Available: www.elsevier.com/locate/tsf
17. A. A. Joraid, "Comparison of electrochromic amorphous and crystalline electron beam deposited WO₃ thin films," *Current Applied Physics*, vol. 9, no. 1, pp. 73–79, Jan. 2009, doi: 10.1016/j.cap.2007.11.012.
18. H. Qu et al., "One-pot preparation of crystalline-amorphous double-layer structured WO₃ films and their electrochromic properties," *Electrochim Acta*, vol. 148, pp. 46–52, Dec. 2014, doi: 10.1016/j.electacta.2014.10.017.
19. B. Yang, P. Miao, and J. Cui, "Characteristics of amorphous WO₃ thin films as anode materials for lithium-ion batteries," *Journal of Materials Science: Materials in Electronics*, vol. 31, no. 14, pp. 11071–11076, Jul. 2020, doi: 10.1007/s10854-020-03656-5.
20. R. Hatel and M. Baitoul, "Nanostructured tungsten trioxide (wo3): Synthesis, structural and morphological investigations," in *Journal of Physics: Conference Series*, Sep. 2019, vol. 1292, no. 1. doi: 10.1088/1742-6596/1292/1/012014.
21. H. Kalhori, M. Ranjbar, H. Salamati, and J. M. D. Coey, "Flower-like nanostructures of WO₃ Fabrication and characterization of their in-liquid gasochromic effect," *Sens Actuators B Chem*, vol. 225, pp. 535–543, Mar. 2016, doi: 10.1016/j.snb.2015.11.044.
22. L. Raveendran, S. Gandhimathynathan, and V. Veerapandy, "Preparation and characterization of tungsten trioxide (WO₃) thin films," *Adv Mat Res*, vol. 678, pp. 32–36, 2013, doi: 10.4028/www.scientific.net/AMR.678.32.
23. A. Karuppasamy and A. Subrahmanyam, "Electron beam induced coloration and luminescence in layered structure of WO₃ thin films grown by pulsed dc magnetron sputtering," *J Appl Phys*, vol. 101, no. 11, 2007, doi: 10.1063/1.2737957.
24. S. Sharma, M. Tomar, N. K. Puri, and V. Gupta, "NO₂ Sensing Properties of WO₃ Thin Films Deposited by Rf-Magnetron Sputtering," *Conference Papers in Science*, vol. 2014, pp. 1–5, Apr. 2014, doi: 10.1155/2014/683219.
25. A. Paliwal, A. Sharma, M. Tomar, and V. Gupta, "Optical properties of WO₃ thin films using surface plasmon resonance technique," *J Appl Phys*, vol. 115, no. 4, Jan. 2014, doi: 10.1063/1.4862962.

© 2023 | Published by IRJSE

Submit your manuscript to a IRJSE journal and benefit from:

- ✓ Convenient online submission
- ✓ Rigorous peer review
- ✓ Immediate publication on acceptance
- ✓ Open access: articles freely available online
- ✓ High visibility within the field

Submit your next manuscript to IRJSE through our manuscript management system uploading at the menu "Make a Submission" on journal website

<https://irjse.in/se/index.php/home/about/submissions>

For enquiry or any query email us: editor@irjse.in



Gaqtap